
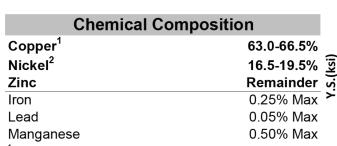


Alloy C752 is an excellent choice for designers considering both functional and decoration applications. Offering a combination of strength, ductility and moderately high work-hardening rate C752 is widely used as both a deep drawing and spring alloy. The added advantage of having a silvery-white color almost identical to that of silver or stainless steel makes C752 valuable for a variety of applications including; flatware, jewelry, medallions and antimicrobial touch surfaces.

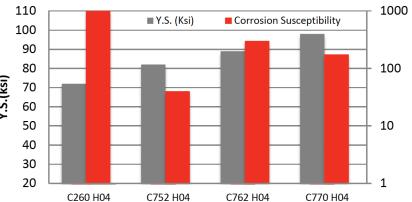

<sup>&</sup>lt;sup>1</sup> Cu includes Ag; Copper plus named elements = 99.5%



**Figure 1:** Comparison of Yield Strength and relative susceptibility to stress corrosion (Mattsson's solution and moist ammonia, 1000 = most susceptible).

| Physical Properties                     |                                  |                        |  |  |  |  |
|---|----------------------------------|------------------------|--|--|--|--|
|   | English Units                    | Metric Units           |  |  |  |  |
| Density                                 | 0.316 lb/in <sup>3</sup> @ 68ºF  | 8.73 g/cm <sup>3</sup> |  |  |  |  |
| Thermal Conductivity                    | 19 BTU-ft/ft <sup>2</sup> -hr-ºF | 33 W/mºK               |  |  |  |  |
| Electrical Resistivity                  | 173 ohm circ mils/ft             | 28.7 microhm-cm        |  |  |  |  |
| Electrical Conductivity (annealed)      | 6% IACS*                         | 0.0348 megamho/cm      |  |  |  |  |
| Modulus of Elasticity                   | 18,000,000 psi                   | 124 kN/mm <sup>2</sup> |  |  |  |  |
| Thermal Capacity(Specific Heat)         | 0.090 Btu/lb/F° @ 68°F           | 377.1 J/kg ⋅ °C @ 20°C |  |  |  |  |
| Coeff. Of Thermal Expansion             | _                                |                        |  |  |  |  |
| 68-572°F (20-300°C)                     | 9.0 PPM/°F                       | 16.2 PPM/°C            |  |  |  |  |
| *International Annealed Copper Standard |                                  | 1                      |  |  |  |  |

| Mechanical Properties |                  |                   |                             |                   |                           |                                 |     |  |  |
|-----------------------|------------------|-------------------|-----------------------------|-------------------|---------------------------|---------------------------------|-----|--|--|
| Temper <sup>1</sup>   | Tensile Strength |                   | Yield Strength <sup>2</sup> |                   | % Elongation <sup>2</sup> | Typical 90° Bend<br>Formability |     |  |  |
|                       | ksi              | N/mm <sup>2</sup> | ksi                         | N/mm <sup>2</sup> |                           | GW/BW <sup>3</sup>              |     |  |  |
| Annealed              | 53-63            | 365-435           | 25                          | 170               | 35                        | -                               | -   |  |  |
| 1/4 Hard              | 58-72            | 400-495           | 45                          | 310               | 24                        | -                               | 0.5 |  |  |
| 1/2 Hard              | 66-80            | 455-550           | 63                          | 435               | 14                        | 0.5                             | 0.8 |  |  |
| 3/4 Hard              | 74-86            | 510-595           | 75                          | 515               | 8                         | 1.0                             | 1.0 |  |  |
| Hard                  | 78-91            | 540-625           | 82                          | 565               | 5                         | 1.5                             | 1.5 |  |  |
| Extra Hard            | 86-98            | 595-675           | 91                          | 625               | 3                         | 2.0                             | 2.0 |  |  |
| Spring                | 90-101           | 620-695           | 93                          | 640               | 1 min                     | 4.0                             | 4.0 |  |  |
| Extra Spring          | 96 min           | 660 min           | 95 min                      | 655 min           | 2 Max                     |                                 |     |  |  |

<sup>&</sup>lt;sup>1</sup> Mechanical properties subject to change. All tempers listed are made to a Tensile Strength specification unless otherwise noted.

<sup>&</sup>lt;sup>2</sup> Ni Values Include Co

<sup>&</sup>lt;sup>2</sup> Nominal Values <sup>3</sup> DATA FOR REFERENCE ONLY. R/T = Bend Radius/Material Thickness <0.016" (0.4mm) thick, 11/16 (17.5mm) wide.