

Material Designation	
EN	CuZn30
UNS*	C26000

\* Unified Numbering System (USA)

Chemical Composition (Reference)	
Cu	70 %
Zn	balance

**Typical Applications**

- Jewellery and metal goods
- Deep drawn parts
- Components for the electrical industry
- Stamped parts
- Connectors

**Physical Properties\***

Electrical Conductivity	MS/m	16
	%IACS	28
Thermal Conductivity	W/(m·K)	126
Coefficient of Electrical Resistance**	10 <sup>-3</sup> /K	1.5
Coefficient of Thermal Expansion**	10 <sup>-6</sup> /K	19.7
Density	g/cm <sup>3</sup>	8.55
Modulus of Elasticity	GPa	114
Specific Heat	J/(g·K)	0.377
Poisson's Ratio		0.34

\* Reference values at room temperature

\*\* Between 0 and 300 °C

**Fabrication Properties**

Capacity for Being Cold Worked	excellent
Machinability	less suitable
Capacity for Being Electroplated	excellent
Capacity for Being Hot-Dip Tinned	excellent
Soft Soldering	excellent
Resistance Welding	good
Gas Shielded Arc Welding	fair
Laser Welding	less suitable

**Corrosion Resistance**

Good resistance to: fresh water, neutral or alkaline solutions, organic compounds as well as land, sea, and industrial atmosphere.

Not resistant to: acids, hydrous sulphur compounds, hydrous ammonia (stress corrosion cracking) in non-stress-relieved condition.


**Mechanical Properties**

Temper		R270	R350	R410	R480	R550	R630
Tensile Strength R <sub>m</sub>	MPa	270–350	350–430	410–490	480–560	550–640	≥ 630
Yield Strength R <sub>p0.2</sub>	MPa	≤ 160	≥ 170	≥ 260	≥ 430	≥ 500	–
Elongation A <sub>50mm</sub>	%	≥ 40	≥ 21	≥ 9	≥ 4	–	–


Temper		H055	H095	H120	H150	H170	H190
Hardness HV		55–90	95–125	120–155	150–180	170–200	≥ 190

Temper		G010	G020	G030	G050	G075
Grain Size	mm	≤ 0.015	0.015–0.030	0.020–0.040	0.035–0.070	0.050–0.100
Hardness HV		≤ 120	≤ 95	≤ 90	≤ 80	≤ 70

**Electrical Conductivity**

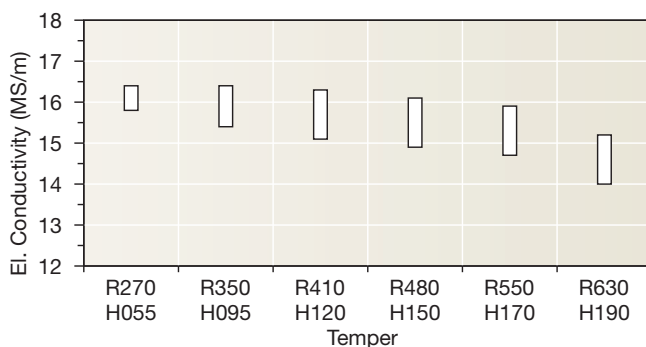



**Bendability (Strip Thickness t ≤ 0.5 mm)**

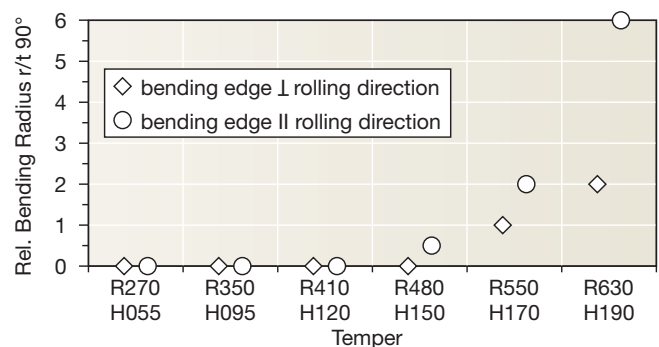

# Wieland-M30


CuZn30  
C26000

## Resistance to Softening

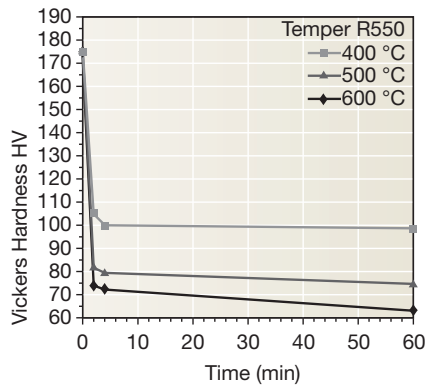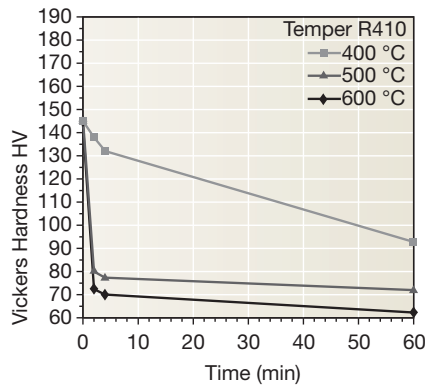

Vickers hardness  
after heat treatment  
(typical values)

## Thermal Stress Relaxation

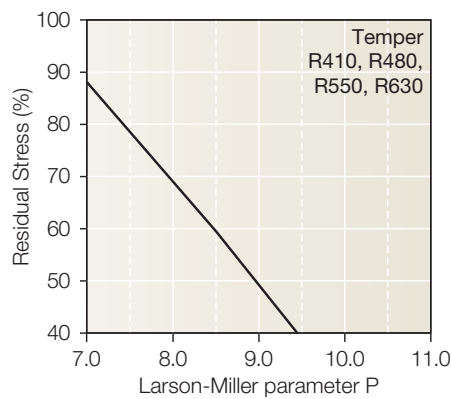

Stress remaining after thermal relaxation as a function of Larson-Miller parameter (F. R. Larson, J. Miller, Trans ASME74 (1952) 765–775) given by:

$$P = (20 + \log(t))(T + 273) \cdot 0.001$$

Time t in hours, temperature T in °C.

Example: P = 9 is equivalent to 1.000 h/118 °C.

Measured on rolled to temper specimens parallel to rolling direction. Total stress relaxation depends on the applied stress level. Furthermore, it is increased to some extent by cold deformation.

## Fatigue Strength

The fatigue strength is defined as the maximum bending stress amplitude which a material withstands for  $10^7$  load cycles under symmetrical alternate load without breaking. It is dependent on the temper tested and is about  $\frac{1}{3}$  of the tensile strength  $R_m$ .

## Types and Formats Available

- Standard coils with outside diameters up to 1400 mm
- Traverse-wound coils with drum weights up to 1.5 t
- Multicoil up to 5 t
- Hot-dip tinned strip
- Contour-milled strip
- Sheet
- Strip and sheet with protective coating

## Dimensions Available

- Strip thickness from 0.10 mm, thinner gauges on request
- Strip width from 3 mm, however min. 10 x strip thickness