

C71500

CuNi30

Cupro-Nickels are among the most attractive, durable and versatile copper alloys manufactured. Offering unique properties that include excellent resistance to biological fouling, corrosion and stress corrosion cracking, these alloys are used in a range of applications from heat exchangers, naval components and condenser tubes of power plants to coinage and touch surfaces in healthcare. Varying nickel additions in these alloys allow designers to benefit from attractive colors ranging from rose gold to silver.

Chemical composition (Reference)

Ni	30 %
Cu	remainder

Physical properties (Reference values at room temperature)


Electrical conductivity	2.7 MS/m	4.6 %IACS
Thermal conductivity	29 W/(m·K)	17 Btu·ft/(ft ² ·h·°F)
Coefficient of electrical resistance*	0.2 10 ⁻³ /K	0.1 10 ⁻³ /°F
Coefficient of thermal expansion*	16.2 10 ⁻⁶ /K	9.0 10 ⁻⁶ /°F
Density	8.94 g/cm ³	0.323 lb/in ³
Modulus of elasticity	152 GPa	22,000 ksi
Specific heat	0.380 J/(g·K)	0.091 Btu/(lb·°F)
Poisson's ratio	0.34	0.34

* Between 0 and 300 °C

Mechanical properties (values in brackets are for information only)

Temper	Tensile strength R _m		Yield strength R _{p0.2}		Elongation A ₅₀ / A ₂ ¹
	MPa	ksi	MPa	ksi	
Annealed	≥ 360	≥ 52	(195)	(28)	(≥ 30)
H01	400-495	58-72	(325)	(47)	(17)
H02	455-550	66-80	(470)	(68)	(6)
H04	515-605	75-88	(540)	(78)	(3)
H06	550-635	80-92	(570)	(83)	(2)
H08	580-650	84-94	(595)	(86)	(≥ 1)

Electrical conductivity

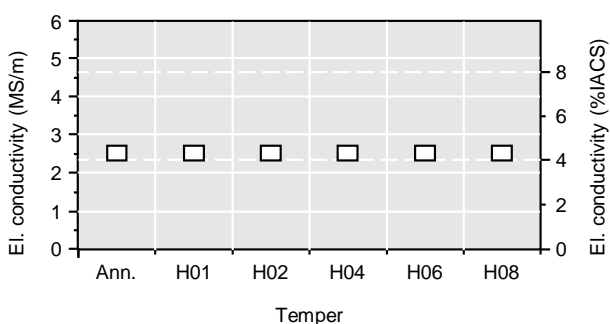

C71500

CuNi30

Fatigue strength

The fatigue strength is defined as the maximum bending stress amplitude which a material withstands for 10^7 load cycles under symmetrical alternate load without breaking. It is dependent on the temper tested and is about 1/3 of the tensile strength R_m .

Types and formats available

- Standard coils with outside diameters up to 1,400 mm
- Traverse-wound coils with drum weights up to 1.5 t
- Multicoil up to 5 t
- Hot-dip tinned strip
- Contour-milled strip

Dimensions available

- Strip thickness from 0.10 mm, thinner gauges on request
- Strip width from 3 mm, however min. 10 x strip thickness

Wieland-Werke AG | Graf-Arco-Straße 36 | 89079 Ulm | Germany
info@wieland.com | wieland.com

Wieland Rolled Products North America | 4803 Olympia Park Plaza, Suite 3000 | Louisville, Kentucky | USA
infona@wieland.com | wieland-rolledproductsna.com

This printed matter is not subject to revision. No claims can be derived from it unless there is evidence of intent or gross negligence. The product characteristics are not guaranteed and do not replace experts' advice.